arXiv:cond-mat/0610648v1 [cond-mat.str-el] 24 Oct 2006

^{31}P-NMR and μSR Studies of Filled Skutterudite Compound SmFe$_4$P$_{12}$: Evidence for Heavy Fermion Behavior with Ferromagnetic Ground State

Kenichi Hachitani[1,2]*, Hideto Fukazawa[1,3], Yoh Kohori[1,3], Isao Watanabe[2],
Yuichi Yoshimitsu[4], Ken-ichi Kumagai[4], Ram Giri[5], Chihiro Sekine[5] and Ichimin Shirotani[5]

[1] *Graduate School of Science and Technology, Chiba University, Chiba 263-8522*
[2] *Advanced Meson Science Laboratory, RIKEN (The Institute of Physical and Chemical Research), Wako, Saitama 351-0198*
[3] *Department of Physics, Faculty of Science, Chiba University, Chiba 263-8522*
[4] *Division of Physics, Graduate School of Science, Hokkaido University, Sapporo 060-0810*
[5] *Department of Electrical and Electronic Engineering, Muroran Institute of Technology, Muroran, Hokkaido 050-8585*

The ^{31}P-NMR (nuclear magnetic resonance) and μSR (muon spin relaxation) measurements on the filled skutterudite system SmFe$_4$P$_{12}$ have been carried out. The temperature T dependence of the ^{31}P-NMR spectra indicates the existence of the crystalline electric field effect splitting of the Sm^{3+} ($J = 5/2$) multiplet into a ground state and an excited state of about 70 K. The spin-lattice relaxation rate $1/T_1$ shows the typical behavior of the Kondo system, *i.e.*, $1/T_1$ is nearly T independent above 30 K, and varies in proportion to T (the Korringa behavior, $1/T_1 \propto T$) between 7.5 K and 30 K. The T dependence deviated from the Korringa behavior below 7 K, which is independent of T in the applied magnetic field of 1 kOe, and suppressed strongly in higher fields. The behavior is explained as $1/T_1$ is determined by ferromagnetic fluctuations of the uncovered Sm^{3+} magnetic moments by conduction electrons. The μSR measurements in zero field show the appearance of a static internal field associated with the ferromagnetic order below 1.6 K.

KEYWORDS: SmFe$_4$P$_{12}$, filled skutterudite, ferromagnetism, heavy fermion system, ^{31}P-NMR (nuclear magnetic resonance) , μSR (muon spin relaxation)

1. Introduction

Filled skutterudite compounds RT_4X_{12} (R: rare earth, actinide; T: Fe, Ru, Os; X: P, As, Sb) crystallize in a body-centered cubic (BCC) structure of the space group $Im\ \bar{3}$ (No. 204).[1] These compounds have recently attracted much attention as improved thermoelectric materials and for their wide variety of electrical and magnetic properties, such as the superconductivity, the heavy fermion (HF) system, the multipolar order, the magnetic order, the metal-insulator (M-I) transition and the non-Fermi-liquid behavior.[2–9]

Among them, SmRu$_4$P$_{12}$ was reported to exhibit an M-I transition at $T_{\rm MI}$ of 16.5 K. Recently, it was demonstrated that the M-I transition accompanies the magnetic octupolar order and that there is the additional antiferromagnetic (AFM) order below 15 K, respectively.[7–12] The SmOs$_4$P$_{12}$ was reported to show the simple AFM order below 4.6 K.[13,14] The SmFe$_4$P$_{12}$ and SmOs$_4$Sb$_{12}$ were reported to exhibit the heavy fermion behavior with ferromagnetic (FM) ground states.[13–17]

In SmFe$_4$P$_{12}$, susceptibility and specific heat measurements show that the Sm ions are in a trivalent state and that the system has an FM transition at the Curie temperature $T_{\rm C}$ of 1.6 K.[13,15] The temperature T dependence of the electric resistivity exhibits the Kondo-lattice behavior (Kondo temperature $T_{\rm K}$ = 30 K), and the electronic specific heat coefficient attains the value of 370 mJ/mole K^2.[13,15] In a BCC structure with the point group of T_h symmetry, the Sm^{3+} ($J = 5/2$) multiplet is split into a doublet Γ_5 and a quartet Γ_{67} by the crystalline electric field (CEF). The specific heat data also suggests the CEF effect splitting of the ground state and the excited state separated by around 70 K.[18] However, the Kondo effect brings the uncertainty in the determination of the ground and the excited states, *i.e.*, we do not know whether the ground state is Γ_5 or Γ_{67}. Indeed, the magnetic entropy associated with the FM order is $0.17R\ln 2$, which is much smaller than the value expected for the case that the ground state is Γ_5.

In this paper, we report the microscopic magnetic properties of SmFe$_4$P$_{12}$ obtained by ^{31}P-NMR (nuclear magnetic resonance) and μSR (muon spin relaxation) measurements. The results of the ^{31}P-NMR Knight shift K and the spin-lattice relaxation rate $1/T_1$ measurements are discussed on the basis of the Kondo screened magnetic moment model. The μSR is ideal for the investigation of the magnetic properties in zero external field.

2. Experimental

The single-phase polycrystalline SmFe$_4$P$_{12}$ has been synthesized by using the high temperature and high pressure method.[13] The sample was crushed into powder for the experiments.

The ^{31}P-NMR has been performed by using phase-coherent pulsed NMR spectrometers and superconducting magnets. The ^{31}P NMR spectra were measured by the convolution of Fourier transform signals of the spin echo which were obtained at 20 kHz interval. The $1/T_1$ was measured with the saturation recovery method in applied magnetic fields of 0.921-33.4 kOe. The nuclear magnetization recovery curve was fitted by a simple exponen-

---

*E-mail address: hachitani@physics.s.chiba-u.ac.jp

tial function as expected for the nuclear spin $I = 1/2$ of ^{31}P nucleus, which allows us to determine a unique $1/T_1$ value at each temperature and field.

The μSR has been performed by implanting pulses of positive surface muons at the RIKEN-RAL Muon Facility in the UK. The direction of the initial muon spin is parallel to the beam line where forward and backward counters were located on the upstream and the downstream sides. The asymmetry parameter $A(t)$ was defined as $A(t) = [F(t) - \alpha B(t)]/[F(t) + \alpha B(t)] - A_{\rm BG}$, where $F(t)$ and $B(t)$ are the total muon events counted by the forward and the backward counters at time t, respectively. The $A_{\rm BG}$ is the background, and α is the calibration factor reflecting the relative counting efficiencies of both counters. In zero field (ZF-) experiments, stray fields at the sample position were compensated within 0.03 Oe by using correction coils, which is small enough for our ZF-μSR measurement.

3. Results and Discussion

Figure 1 shows the ^{31}P-NMR spectra at several temperatures in the applied field of 94.063 kOe. The line shape of the spectra at high temperatures shows a powder pattern with a nearly uniaxial Knight shift distribution for nuclear spin $I = 1/2$. However, the line shape gradually changes and deviates from the uniaxial powder pattern with decreasing temperature. The change of the line shape becomes remarkable below 70 K. The spectra were analyzed by taking into account of the powder average of K anisotropy and the excess Gaussian broadening. The K is expressed as

$$K = K_{\rm iso} + K_1(3\cos^2\theta - 1) - K_2(\sin^2\theta\cos 2\phi), \quad (1)$$

where the $K_{\rm iso}$ represents an isotropic term, K_1 represents a uniaxial term, and K_2 represents the deviation from the uniaxial symmetry.

The T dependence of $K_{\rm iso}$, $-K_1$ and K_2 are shown in Figs. 2 and 3, respectively. The T dependence of $K_{\rm iso}$ is remarkably different from that of the bulk susceptibility χ. The $K_{\rm iso}$ rapidly increases with increasing temperature, and has a broad maximum around 120 K and then decreases slightly at higher temperatures. To clarify the T dependence, $K_{\rm iso}$ is plotted against χ, as seen in Fig. 4. The K-χ plot shows the T dependence of the transferred hyperfine coupling as

$$K_{\rm iso} = \frac{A_{\rm hf}}{N_{\rm A}\mu_{\rm B}}\chi, \quad (2)$$

where $N_{\rm A}$ and $\mu_{\rm B}$ are the Avogadro number and the Bohr magneton, respectively. It is noticed that the K-χ plot is linear in the T ranges of 25-120 K and above about 150 K. The hyperfine coupling constants $A_{\rm hf}$ were estimated about -0.71 kOe/$\mu_{\rm B}$ below 120 K and about $+0.74$ kOe/$\mu_{\rm B}$ above 150 K from the K-χ plot by adopting the formula (2). Considering $T_{\rm K} = 30$ K in this system, the change in the hyperfine coupling around 120 K is reasonably attributed to the CEF splitting. The change of a hyperfine field associated with a CEF effect was reported in other system.[19]

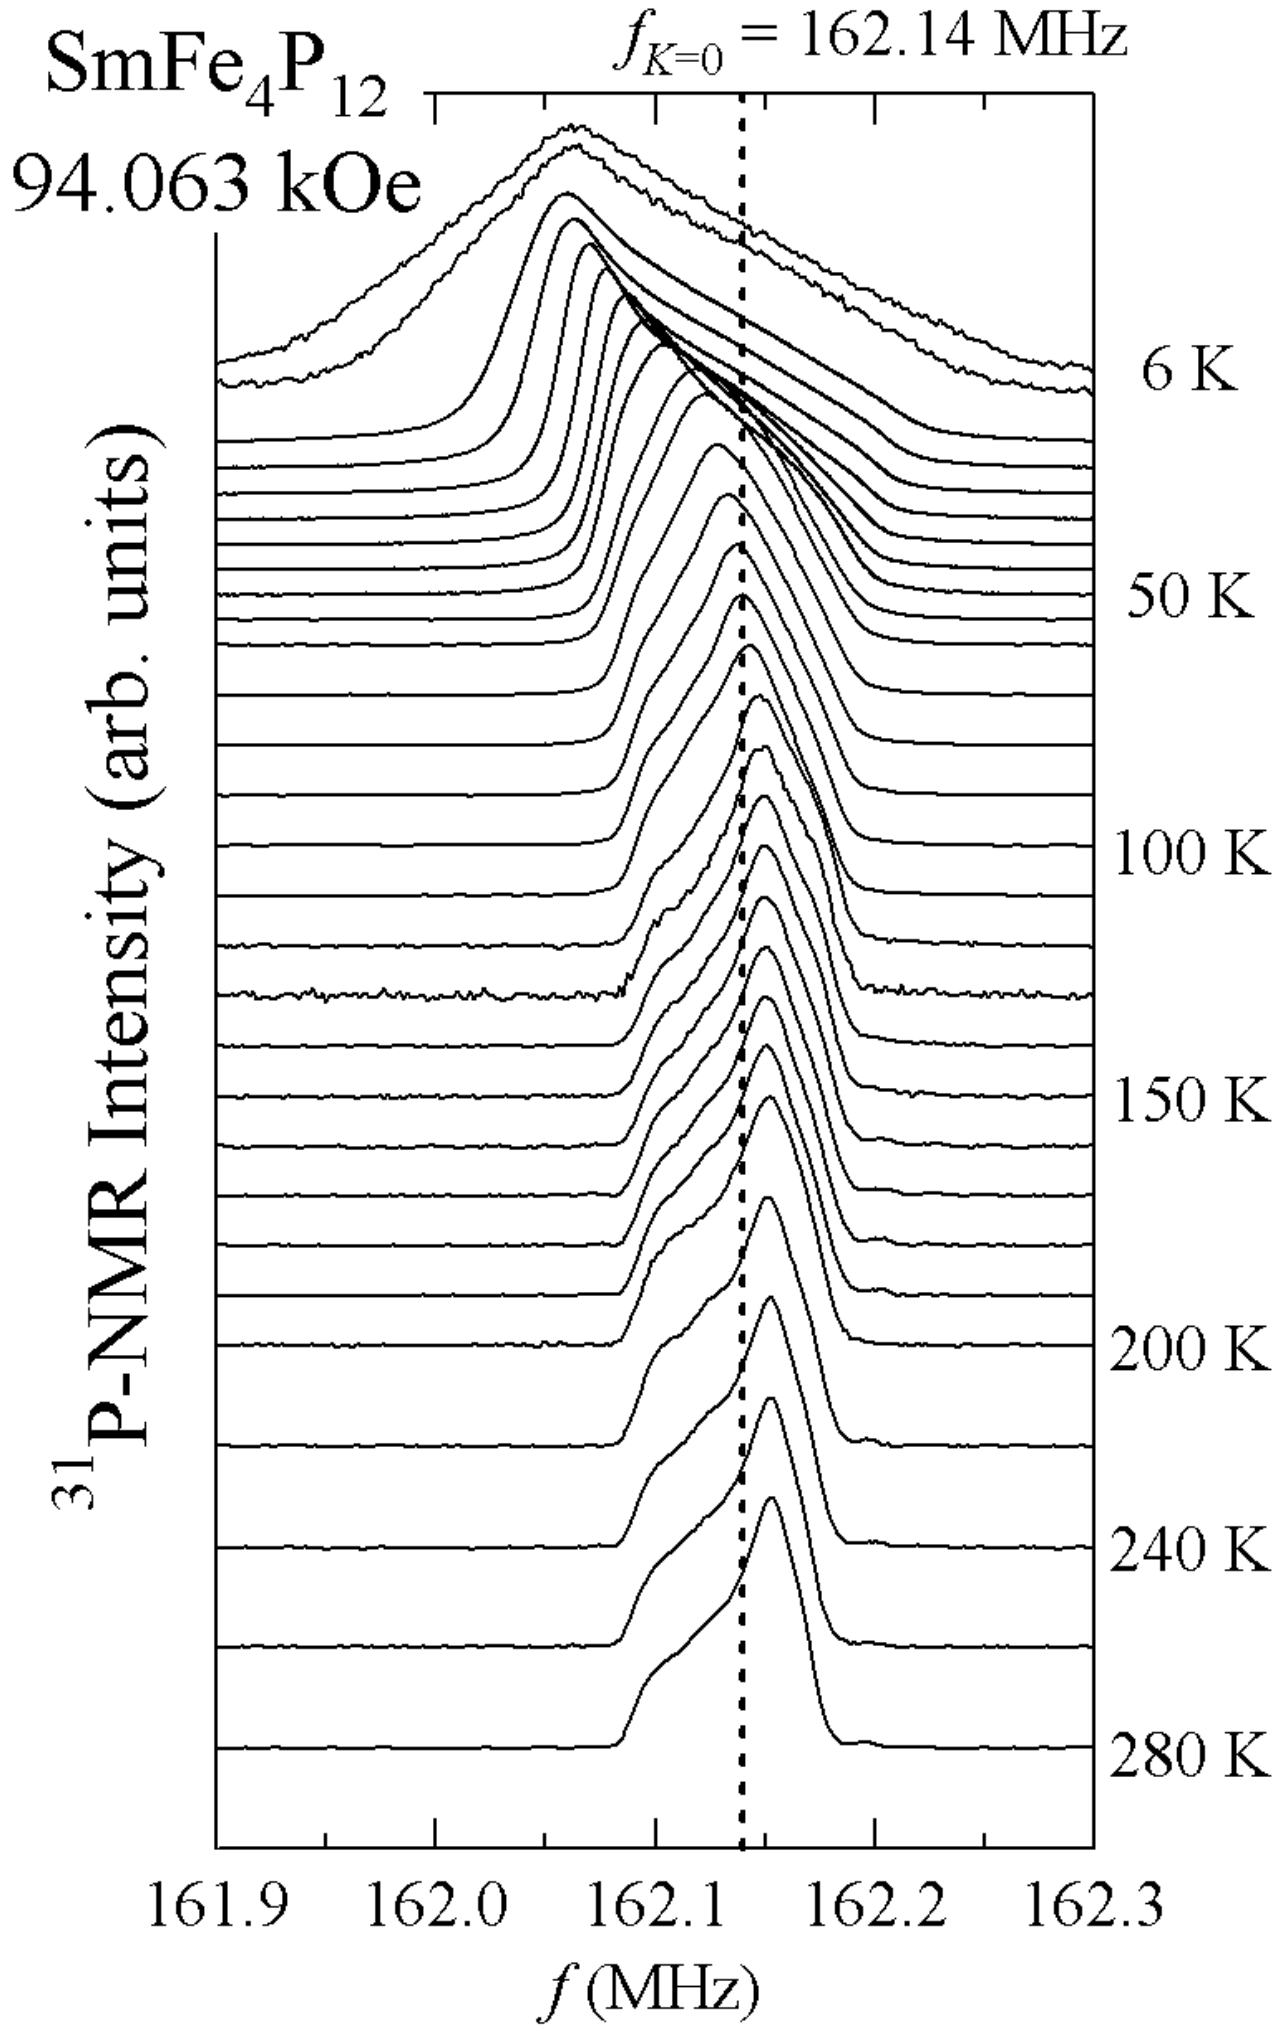

Fig. 1. ^{31}P-NMR spectra at several temperatures in the applied magnetic field of 94.063 kOe. The broken line shows the resonance frequency of 162.14 MHz at $K = 0$ estimated from the nuclear gyromagnetic ratio of the ^{31}P nucleus.

The K_1 is nearly T independent in the whole T region with the value of about -0.015 %. The K_2 decreases with increasing temperature below about 70 K, and decreases very gradually at higher temperatures (0.0059 % at 280 K). One origin of the anisotropic hyperfine coupling is the the direct dipolar coupling of Sm^{3+} magnetic moments and ^{31}P nuclear spins. The lattice sum calculation predicts nearly uniaxial Knight shift to be $K_1 \simeq 0.014$ % and $K_2 \simeq 0.0017$ % at 280 K. These results are shown in Table I including the experimental results. Though the uniaxial anisotropy is observed in our system at high temperatures, K_1 has the opposite sign. This result indicates that the hyperfine mechanism can not be explained by only the direct dipolar coupling even at sufficiently high temperatures (280 K). The nearly same magnitude of K_2 at high temperatures between the experimental and the calculated values is accidental. This suggests that another hyperfine field mechanism contributes to the anisotropic Knight shift. The hybridization of the Sm-4f orbital with the P-3p orbital makes spin polarizations at P-3p spins, which induces the anisotropic field via the dipolar coupling of the P-3p spins and ^{31}P nuclei. The sum of these contributions would explain the observed values. The change of the

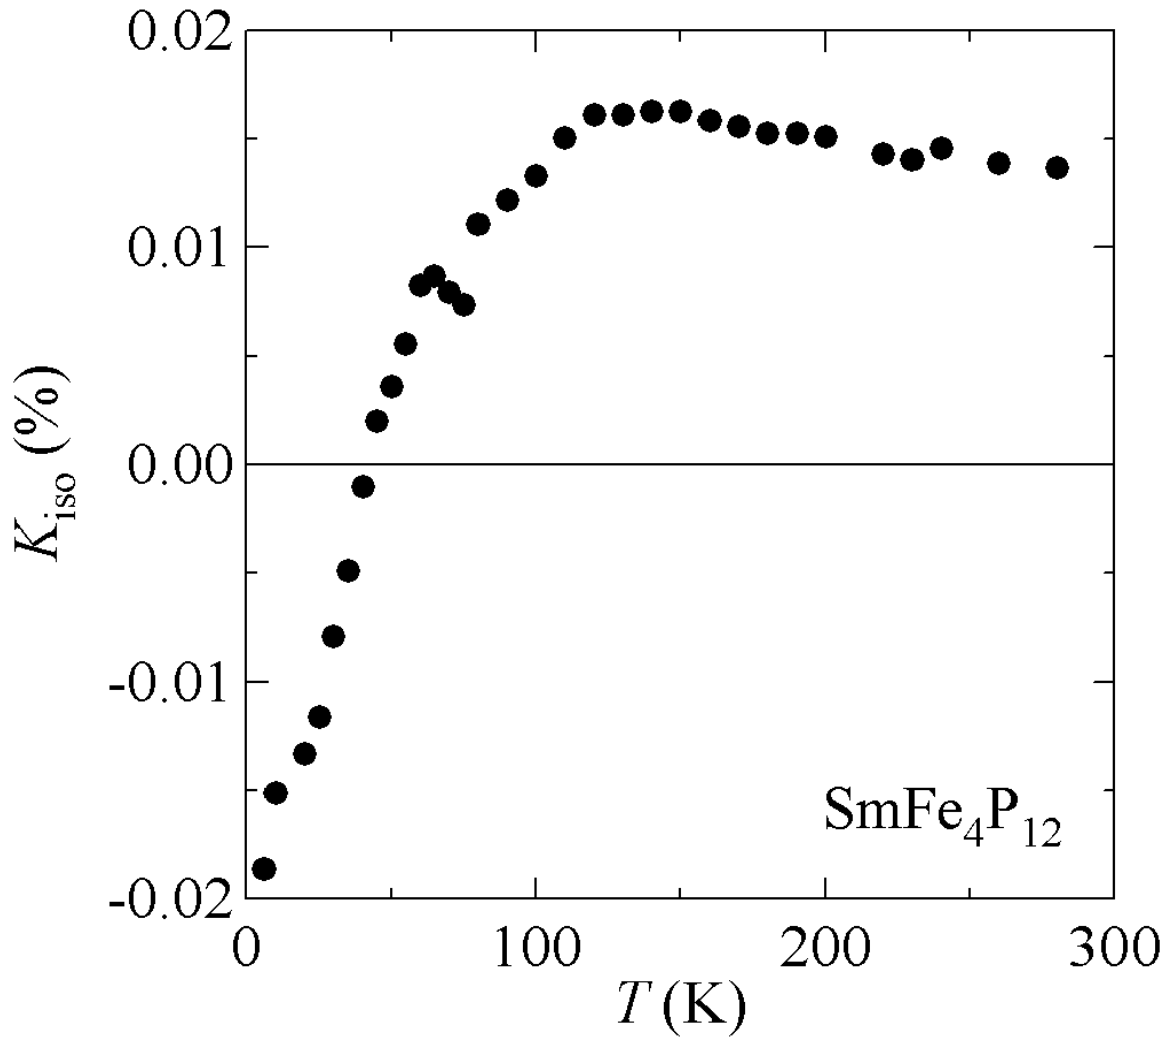

Fig. 2. Temperature dependences of $K_{\rm iso}$

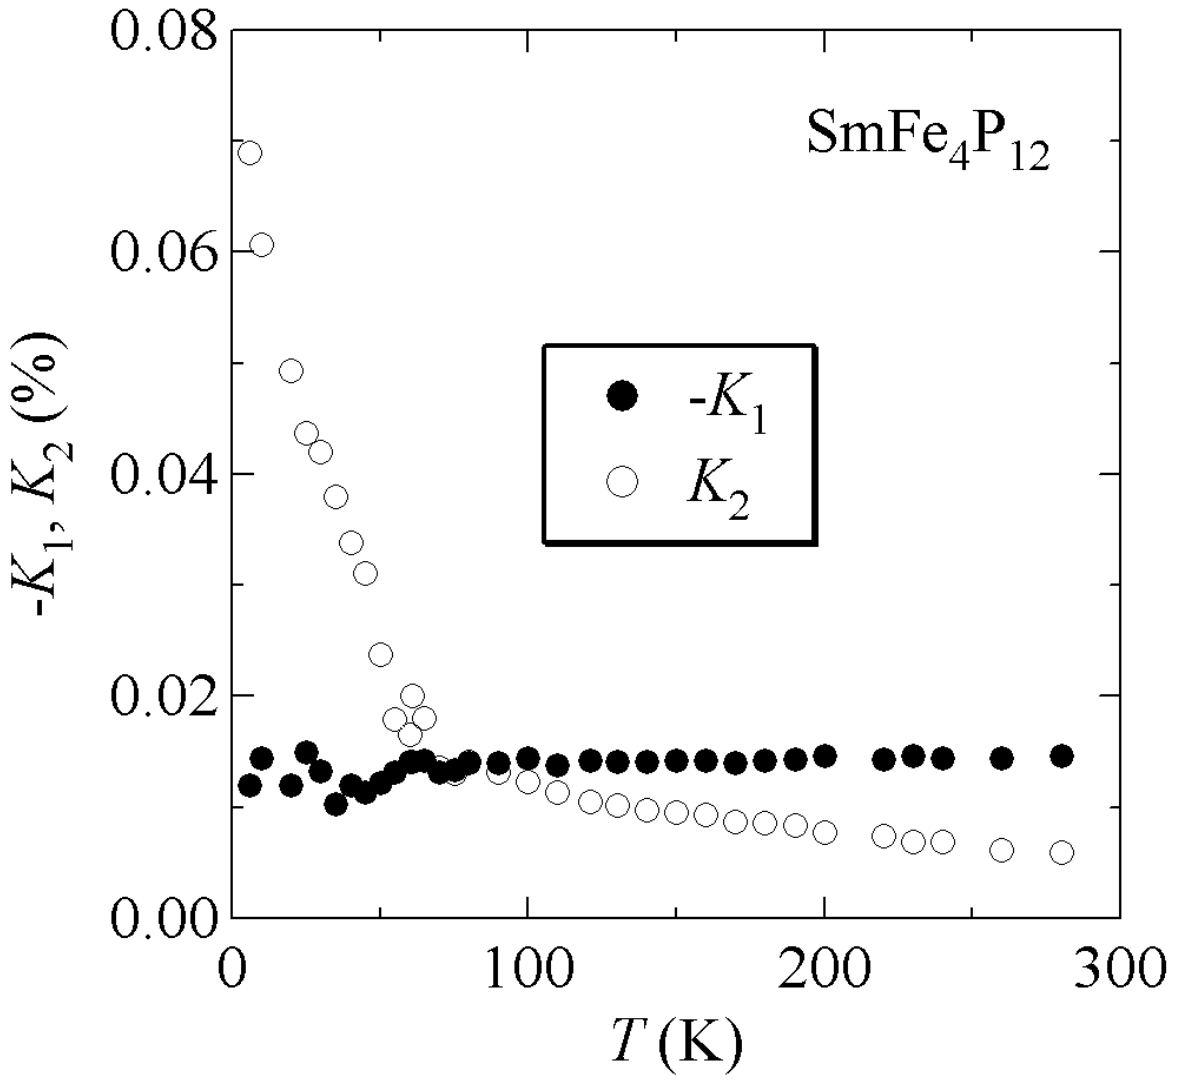

Fig. 3. Temperature dependence of $-K_1$ (closed circles) and K_2 (open circles).

spectra below 70 K is represented by the increase of K_2 which reflects the CEF splitting of about 70 K.[18] The change of a Sm-4f orbital shape occurs associated with the thermal excitation of the CEF levels and modifies the hybridization of the Sm-4f and the ligand P orbitals. For the evaluatation of the ligand spin polarization, a complete solution of the hybridization process is required. The analysis of the spectra is an open problem for future works.

Figure 5 shows the T dependence of $1/T_1$ in several applied fields. The T_1 tends to become long with decreasing temperature. Above 30 K, the weak T dependence was observed. This is attributed to the relaxation by the 4f localized moments of the Sm ions. We evaluated the contribution of the conduction electrons by $1/T_1$ of the nonmagnetic LaFe$_4$P$_{12}$, which is much smaller than the value observed in SmFe$_4$P$_{12}$.[20] After subtracting this contribution, the corrected $1/T_1$ has much weaker T dependence, which is shown as "$(1/T_1)_{\rm 4f}$" in Fig. 5. We observed the Fermi liquid (the Korringa behavior, $T_1T \sim$ constant) in the temperature range of 7.5-30 K, which indicates the major part of the Sm 4f-electrons to be itinerant by the hybridization of the conduction electrons below $T_{\rm K}$.

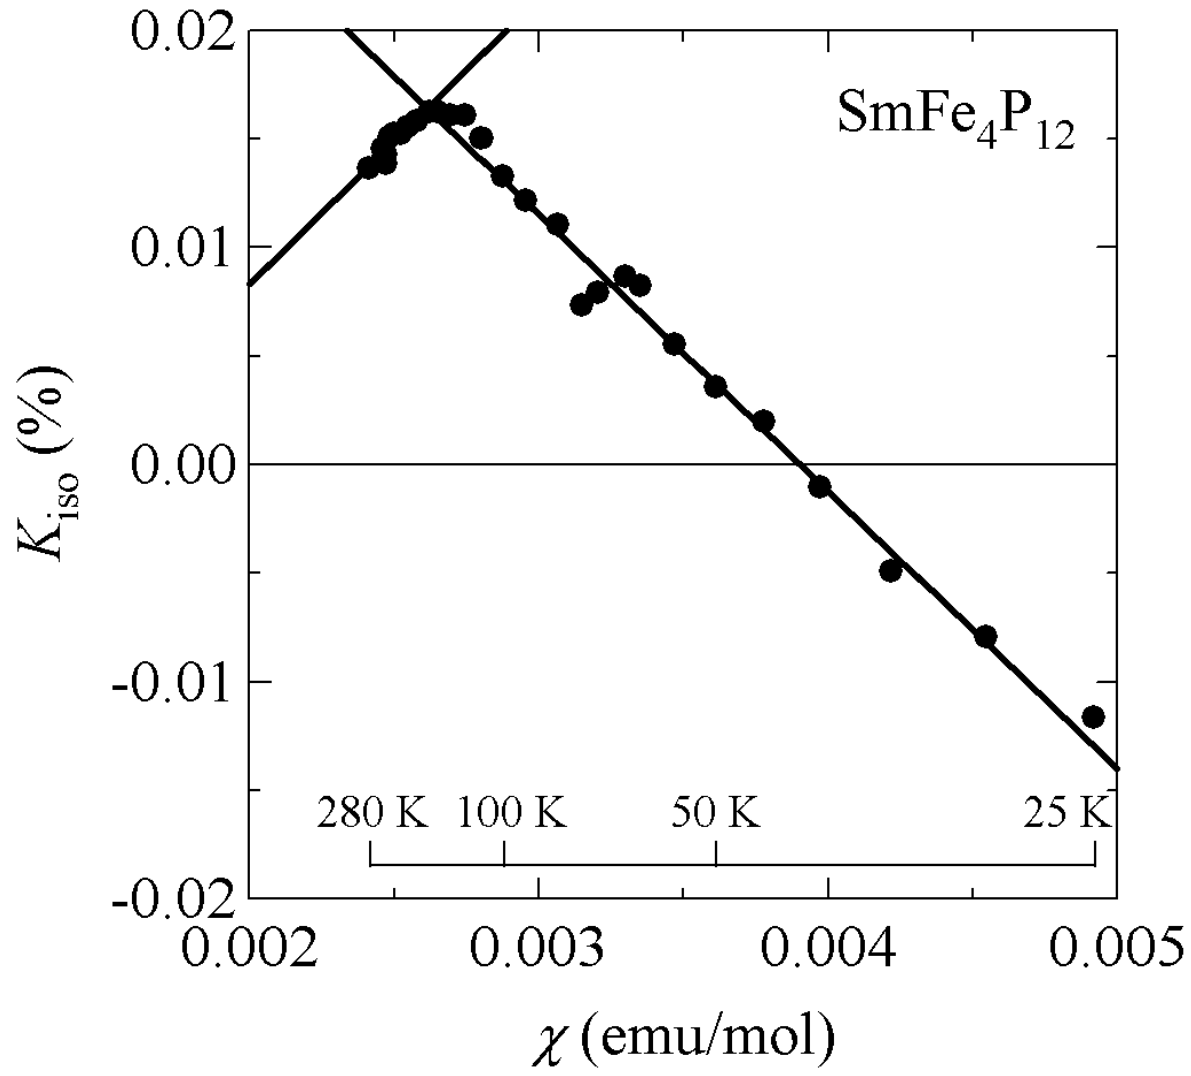

Fig. 4. Bulk susceptibility dependence of $K_{\rm iso}$ (K-χ plot). The solid lines show the linear function of χ expressed by the formula (2). Some temperatures are also shown corresponding to χ.

Table I. Experimental and the dipolar calculated values of K_1 and K_2 at the temperature of 280 K.

	K_1 (%)	K_2 (%)
Experimental	−0.015	0.0059
Calculated	0.014	0.0017

The $1/T_1$ at 0.921 kOe is nearly T independent above $T_{\rm C}$, and rapidly decreases at lower temperatures. The rapid decrease suggests the existence of a phase transition in ZF. The critical slowing-down phenomenon of $1/T_1$ might be suppressed even by the small external field. We estimated $1/T_1$ on the presumption that the Kondo screened Sm^{3+} moments $\sim$0.2$\mu_{\rm B}$ coupled by the ferromagnetic exchange interactions.[15] The $1/T_1$ is expressed as

$$\frac{1}{T_1} = \frac{\sqrt{2\pi}J(J+1)Z(A/Z)^2}{3\hbar^2\omega_e} \simeq \frac{\omega_n^2}{\omega_e}, \tag{3}$$

where

$$\omega_n = \frac{AJ}{\hbar} = \gamma H_{\rm int}, \quad H_{\rm int} = H_{\rm hf}\mu, \tag{4}$$

$$\omega_e = \frac{2}{3}\frac{J_{\rm exc}^2}{\hbar^2}ZJ(J+1), \quad J_{\rm exc} = \frac{3k_{\rm B}T_{\rm C}}{2ZJ(J+1)}, \tag{5}$$

J is the quantity of the angular momentum of the Sm ions, Z is the number of the nearest neighbor Sm ions, $\hbar$ is the Planck constant divided by 2π, γ is the nuclear gyromagnetic ratio of the ^{31}P nucleus, $H_{\rm int}$ is the internal

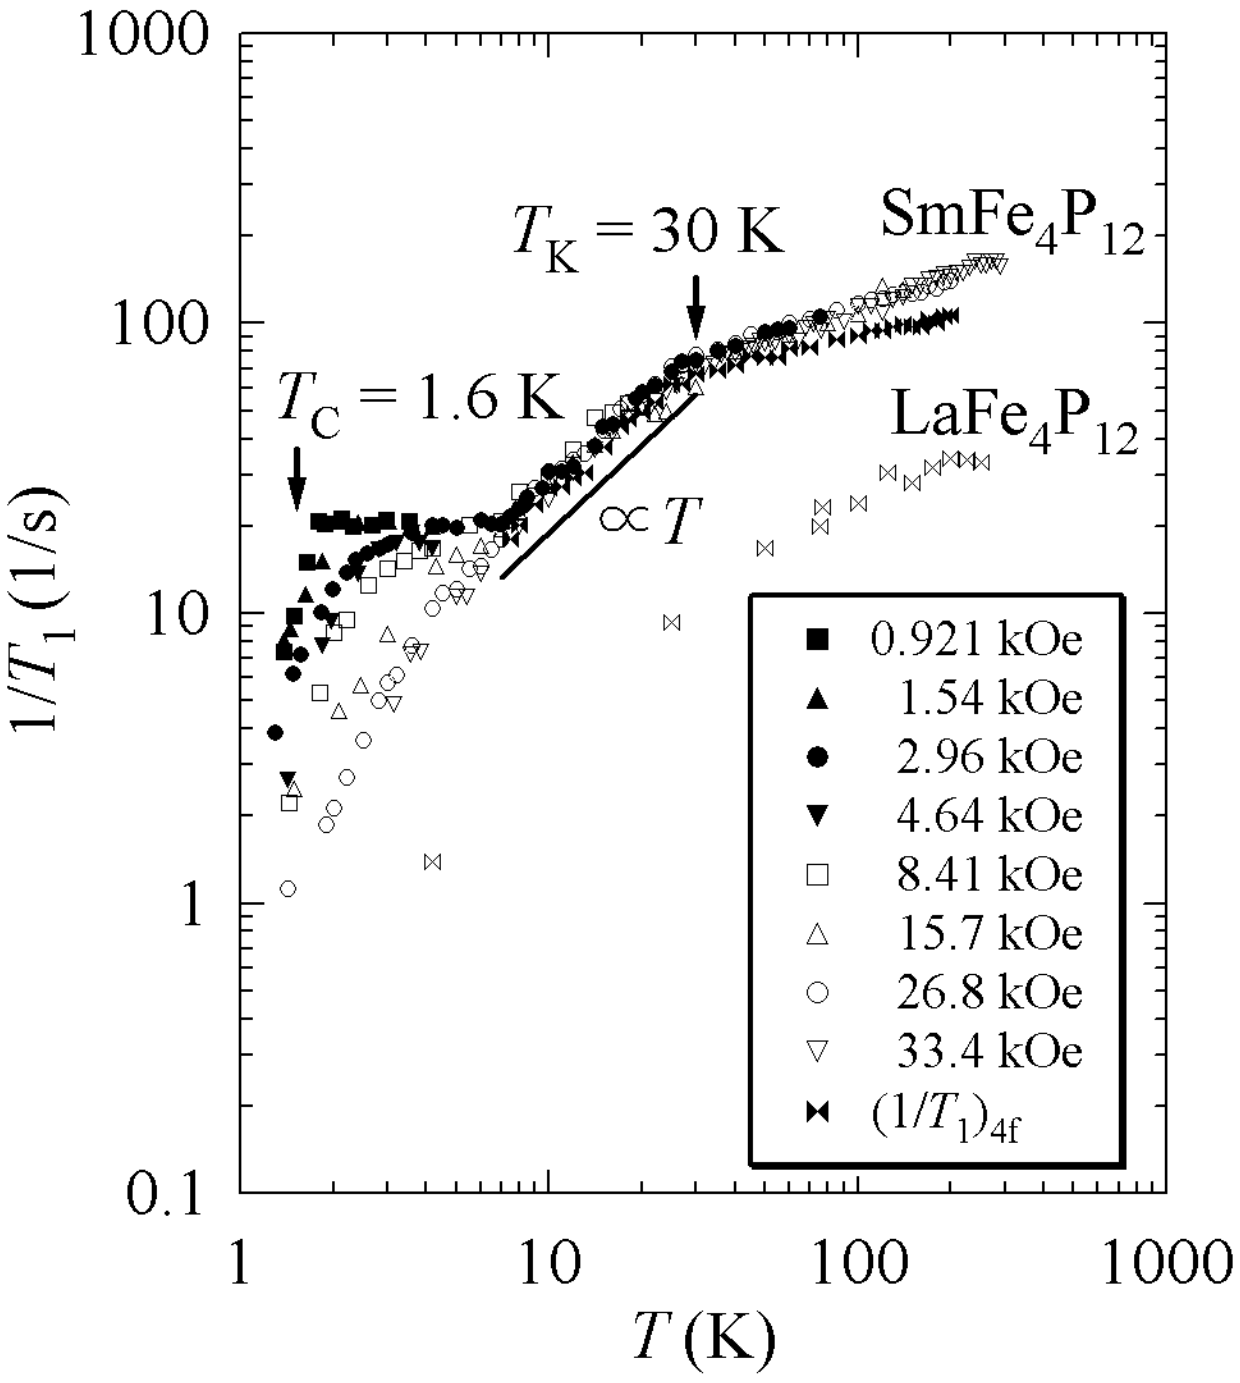

Fig. 5. Temperature dependence of $1/T_1$ in several applied magnetic fields. The $1/T_1$ of nonmagnetic LaFe$_4$P$_{12}$ is also shown as a reference.[20] "$(1/T_1)_{4f}$" is obtained by subtracting $1/T_1$ of LaFe$_4$P$_{12}$ from that of SmFe$_4$P$_{12}$.

field made by the 4f localized moments of the Sm ions at the ^{31}P spins, μ is the saturated moment at 1.4 K, $J_{\rm exc}$ is the ferromagnetic exchange interaction energy, and $k_{\rm B}$ is the Bolzmann constant. The estimated value of $1/T_1$ is about 11.6 1/s, which is close to the experimental values. This result suggests that the origin of the ferromagnetic ground state would be due to the uncovered 4f local moments of the Sm^{3+} by the conduction electrons. The value of $1/T_1$ at low T decreases rapidly with increasing field. The coupling of the uniform ferromagnetic fluctuations and external field strongly suppresses $1/T_1$.

It is important to carry out ZF-measurements to identify the anomaly around $T_{\rm C}$ as a phase transition. However, it is impossible to perform ^{31}P-NMR in ZF, since the ^{31}P nucleus (I=1/2) has no quadrupole moment. Hence, we carried out ZF-μSR to confirm the phase transition.

Figure 6 shows the ZF-μSR time spectra at several temperatures. Below $T_{\rm C}$, $A(t)$ rapidly decreases, and the muon-spin precession was observed as seen clearly in Fig 7. This indicates that the system has a magnetically ordered ground state. The internal field of about 650 Oe at the muon site was estimated from the precession frequency by the formula (6). Above $T_{\rm C}$, $A(t)$ gradually decreases with t where muon-spins depolarize slowly by transferred magnetic fields from dynamically fluctuating Sm moments and nuclear moments.

The spectra were analyzed by a multi-components function expressed by the formula

$$A(t) = A_1 e^{-\lambda_1 t} + A_2 e^{-\lambda_2 t} + A_3 e^{-\lambda_3 t}\cos(\omega t + \theta). \quad (6)$$

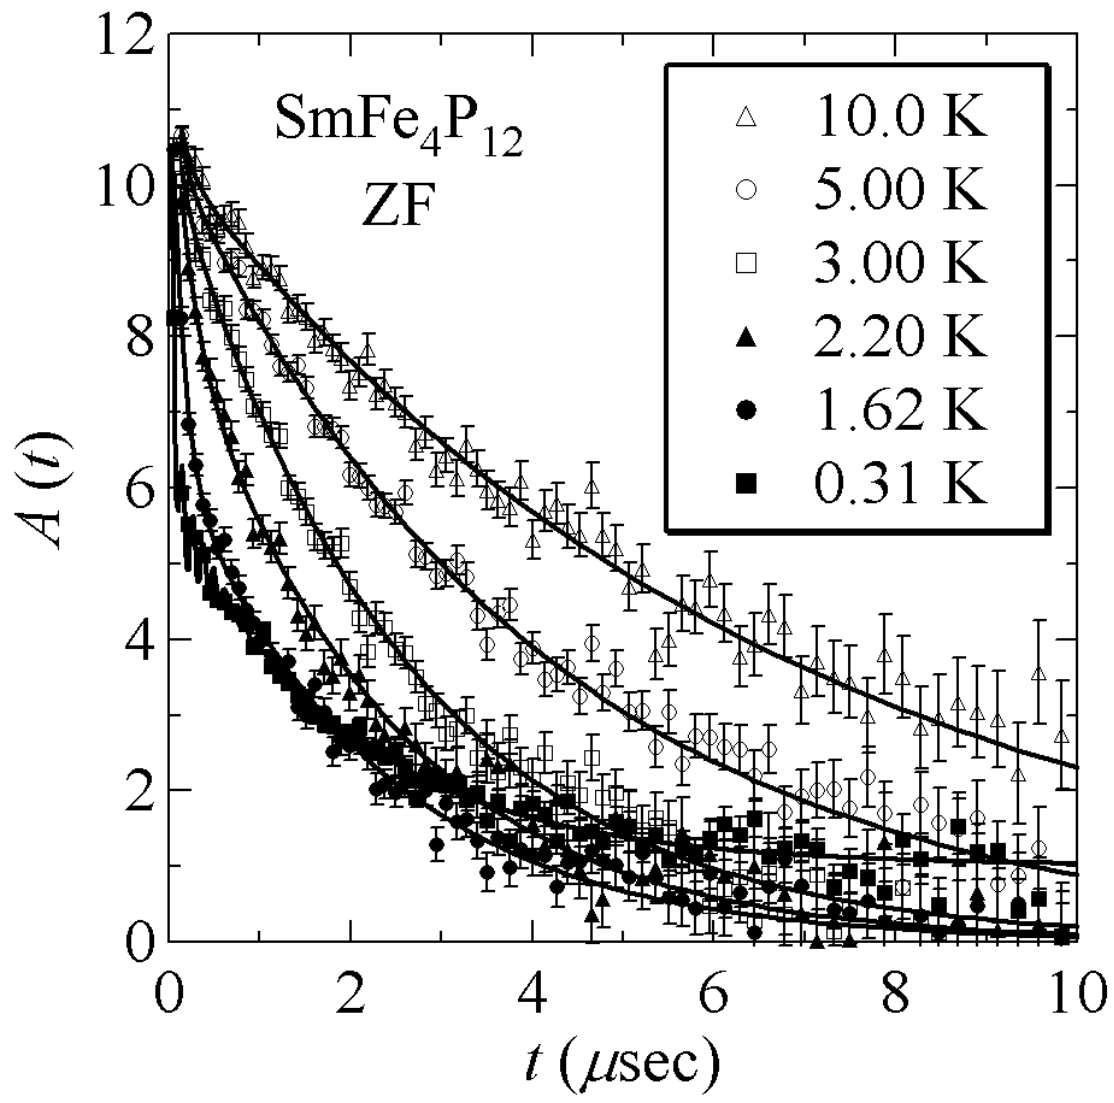

Fig. 6. ZF-μSR time spectra at several temperatures. The solid lines show the best-fit results by the formula (6).

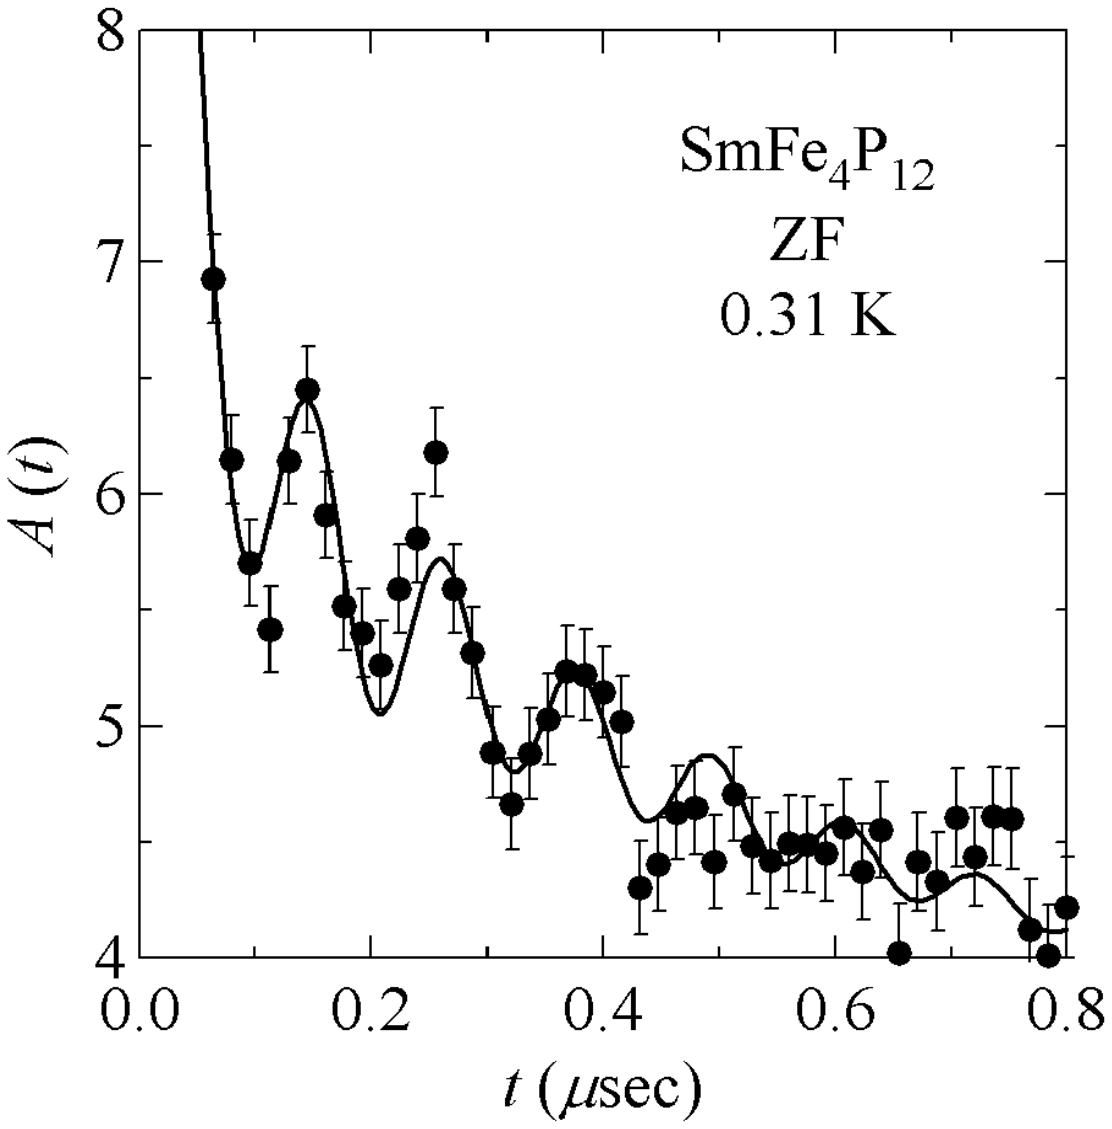

Fig. 7. ZF-μSR time spectrum at the temperature of 0.31 K, which is obtained at a high time resolution. The solid line shows the best-fit results by the formula (6).

The first and the second terms simply represent the components of the rapid and the slow depolarizations, respectively. The third term describes the precession component. The parameters of A_1, A_2, A_3 are the initial asymmetries at $t = 0$, the λ_1, λ_2, λ_3 are the muon-spin depolarization rates, and ω, θ are the frequency and the phase of the precession, respectively. The spectra above 1 K which have no precession were analyzed without the third term. Figures 8 and 9 show the T dependence of A_1, λ_1 and A_2, λ_2 above 1 K obtained from the analysis, respectively. It is noted that the sum of A_1 and A_2 is the constant value of $A(0)$. The spectra above 3 K are almost

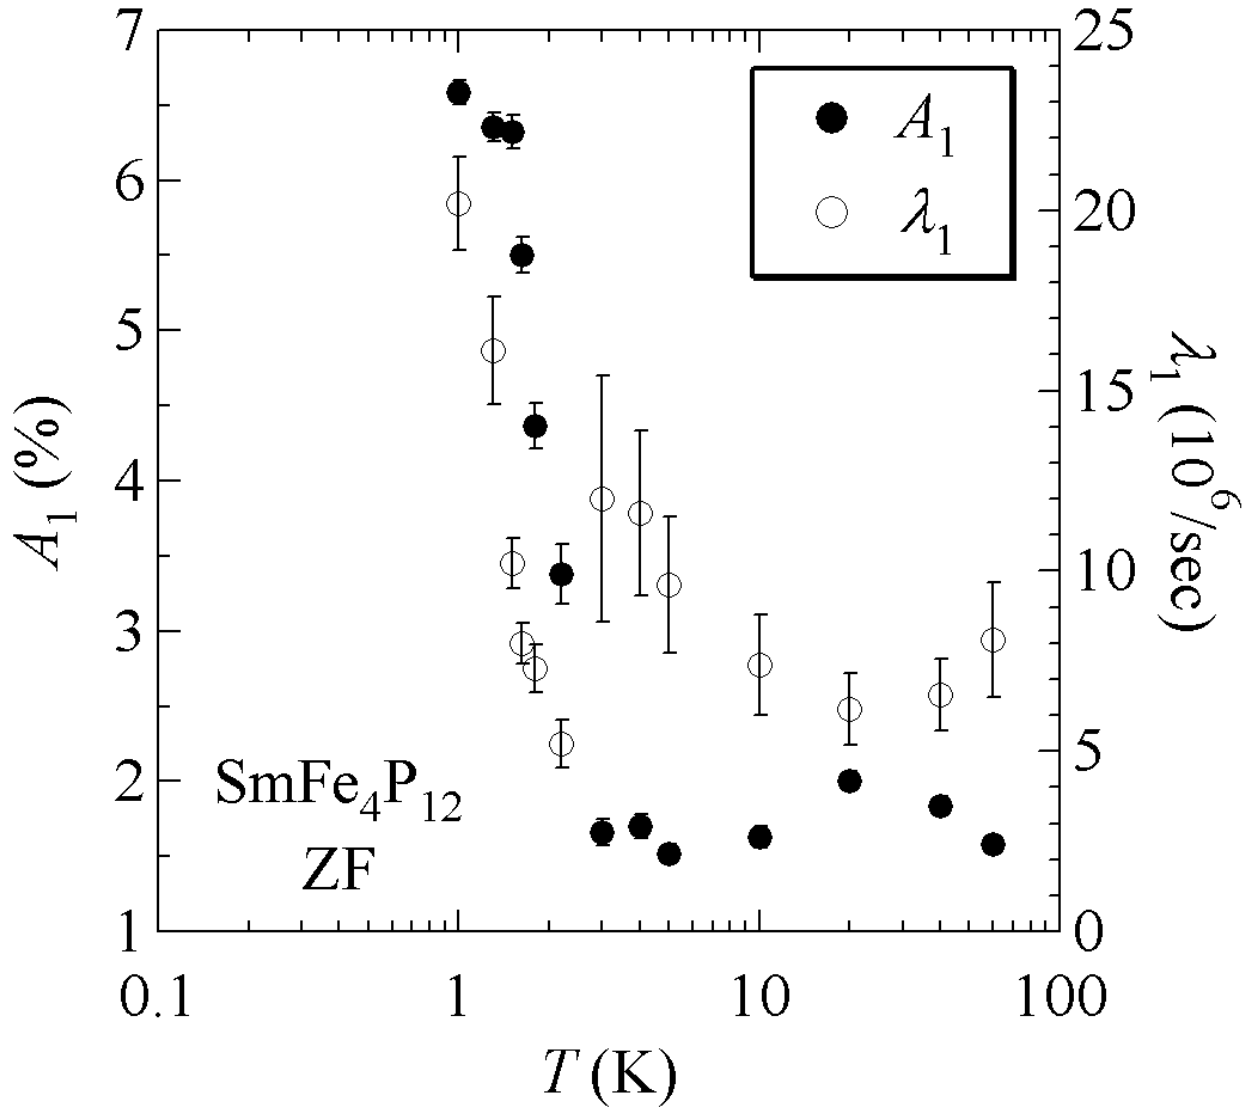

Fig. 8. Temperature dependence of A_1 (closed circles, left axis) and λ_1 (open circles, right axis) above 1 K obtained from the best-fit results shown as the solid lines in Fig. 6.

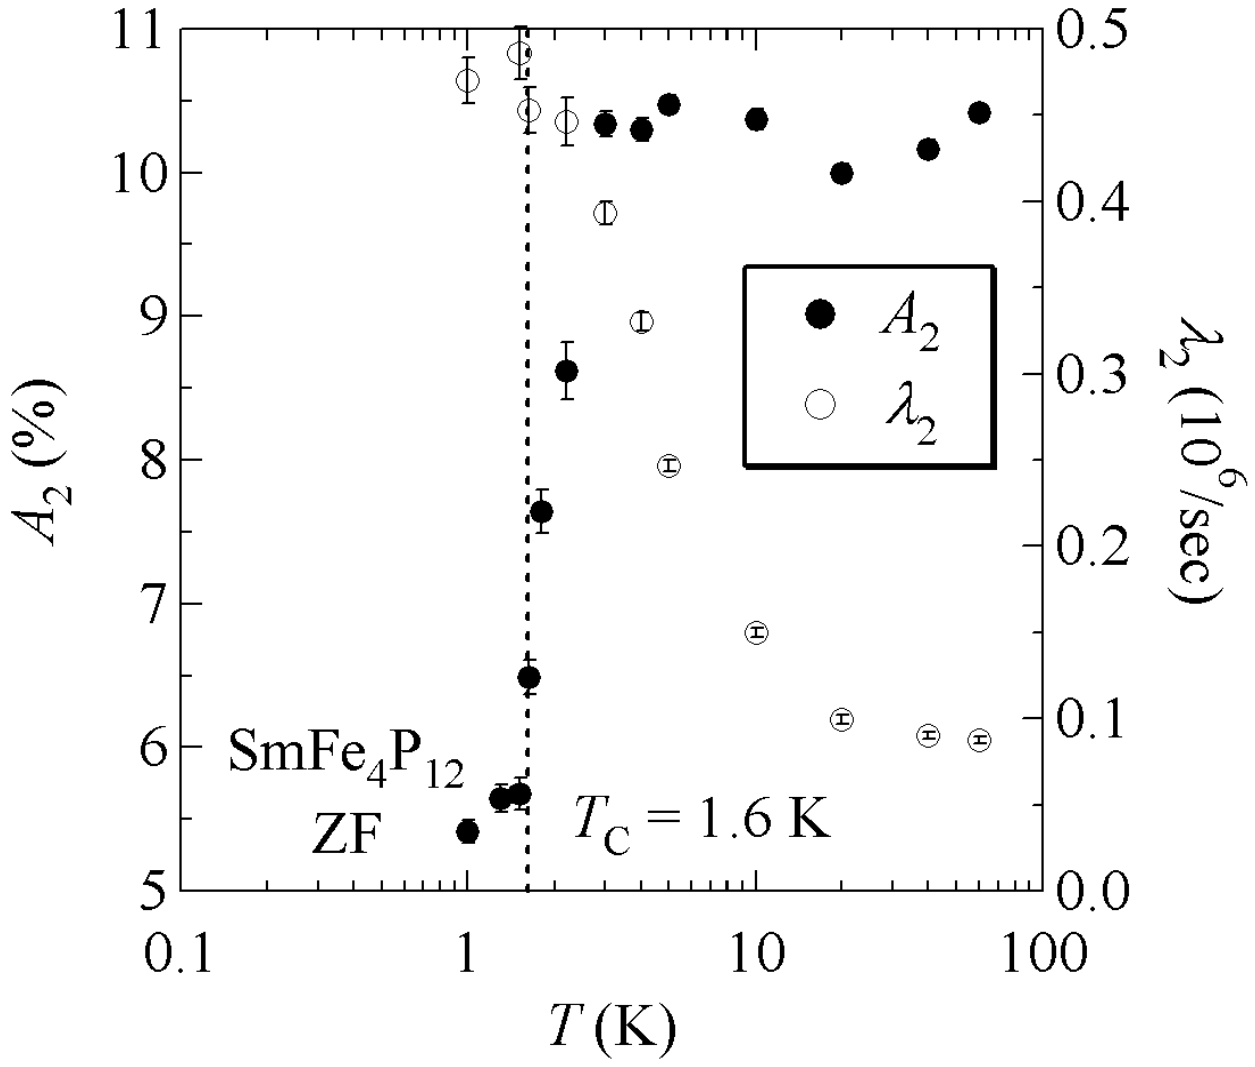

Fig. 9. Temperature dependence of A_2 (closed circles, left axis) and λ_2 (open circles, right axis) above 1 K obtained from the best-fit results shown as the solid lines in Fig. 6.

dominated by only the second term as seen in A_1 and A_2 where the spectra almost follow a single exponential function. Hence, the absolute values of A_1 (corresponding to A_2) and λ_1 above 3 K are not so intrinsic, and the value of A_1 should be 0 idealy. Below 3 K, the first term (rapid depolalization) represents the relaxation by both static and dynamical components which develop below the temperature. Then, we forcus our attention on λ_2 of the second term to discuss the dynamical component.

As seen in Fig. 9, clear anomalies were observed in both A_2 and λ_2 around T_C. The rapid decrease of A_2 corresponds to the rapid increase of A_1. The appearance of the fast relaxation behavior suggests the development of a static internal field attributed to the existence of a magnetic order. Considering that the slow relaxation of the spectra is due to a dynamical component, the peak in λ_2 arises from the critical slowing down behavior of the Sm moments around T_C. The observation of the critical slowing down behavior seems to contradict that of $1/T_1$ by ^{31}P-NMR. One reason would be due to the time-window difference of each probe. The gyromagnetic ratio of the muon is two orders of the magnitude larger than that of ^{31}P nucleus. Hence, μSR is much sensitive to higher frequency components of magnetic fluctuations, which makes the broad temperature dependence of λ_2. It is noteworthy that the behavior of λ_2 is not due to the inhomogeneity of the sample because the sample used in this measurement had been well characterized by other macroscopic measurements.

Though the bahavior of A_2 and λ_2 is obtained qualitatively, this is consistent with the results of ^{31}P-NMR and other measurements.[13,15,18] Indeed, these behavior was also observed around T_{MI} in $SmRu_4P_{12}$ where the magnetic order below T_{MI} has been confirmed by previous μSR measurements.[8] The most important point of this ZF-μSR result of $SmFe_4P_{12}$ is the observation of the muon-spin precession below T_C. These results conclude that the magnetic order occurs below T_C, and support the ^{31}P-NMR results which could not be obtained in ZF.

The FM fluctuations around T_C in finite fields and the existence of a magnetic phase transition at T_C in ZF were observed by means of ^{31}P-NMR and μSR, respectively. Therefore, an FM phase transition at T_C in $SmFe_4P_{12}$ has been confirmed.

4. Conclusions

The ^{31}P-NMR in external fields and the ZF-μSR studies on $SmFe_4P_{12}$ have been carried out. These results show the existence of the CEF effect, the HF behavior below T_K of 30 K and the FM order below T_C of 1.6 K.

Acknowledgments

The authors would like to thank K. Matsuhira and T. Hotta for their useful discussions. This work was supported by a Grant-in-Aid for Scientific Research from the Ministry of Education, Sport, Science and Culture of Japan (no. 17740212). The μSR work was supported by the Toray Science Foundation and the Joint Project of Japan Society for the Promotion of Science. The work at Muroran Institute of Technology was supported by a Grant-in-Aid for Scientific Research in Priority Area "Skutterudite" (no. 15072201) of the Ministry of Education, Culture, Sports, Science and Technology, Japan.

1) W. Jeitschko and D. Braun: Acta Crystallogr. Sect. B **33** (1977) 3401.
2) I. Shirotani, T. Uchiumi, K. Ohno, C. Sekine, Y. Nakazawa, K. Kanoda, S. Todo and T. Yagi: Phys. Rev. B **56** (1997) 7866.
3) D. A. Gajewski, N. R. Dilley, E. D. Bauer, E. J. Freeman, R. Chau, M. B. Maple, D. Mandrus, B. C. Sales and A. H. Lacerda: J. Phys.: Condens. Matter **10** (1998) 6973.
4) M. S. Torikachvili, J. W. Chen, Y. Dalichaouch, R. P. Guertin, M. W. McElfresh, C. Rossel, M. B. Maple and G. P. Meisner: Phys. Rev. B **36** (1987) 8660.
5) C. Sekine, T. Uchiumi, I. Shirotani and T. Yagi: Phys. Rev.

Lett. **79** (1997) 3218.

6) N. Takeda and M. Ishikawa: J. Phys.: Condens. Matter **13** (2001) 5971.

7) M. Yoshizawa, Y. Nakanishi, M. Oikawa, C. Sekine, I. Shirotani, S. R. Saha, H. Sugawara and H. Sato, J. Phys. Soc. Jpn. **74** (2005) 2141.

8) K. Hachitani, H. Fukazawa, Y. Kohori, I. Watanabe, C. Sekine and I. Shirotani: Phys. Rev. B **73** (2006) 052408.

9) K. Hachitani, H. Amanuma, H. Fukazawa, Y. Kohori, K. Koyama, K. Kumagai, C. Sekine and I. Shirotani: to be published in J. Phys. Soc. Jpn. **75** (2006).

10) C. Sekine, T. Uchiumi, I. Shirotani and T. Yagi: *Science and Technology of High Pressure*, ed. M. H. Manghnant *et al.* (Universities Press, Hyderabad, 2000) 826.

11) K. Matsuhira, Y. Hinatsu, C. Sekine, T. Togashi, H. Maki, I. Shirotani, H. Kitazawa, T. Takamasu and G. Kido: J. Phys. Soc. Jpn. **71** (2002) Supple., 237.

12) C. Sekine, I. Shirotani, K. Matshira, P. Haen, S. De Brion, G. Chouteau, H. Suzuki and H. Kitazawa: Acta Physica Polonica B **34** (2003) 983.

13) R. Giri, Y. Shimaya, C. Sekine, I. Shirotani, K. Matsuhira, Y. Doi and Y. Hinatsu: Physica B **329-333** (2003) 458.

14) K. Hachitani, H. Fukazawa, Y. Kohori, I. Watanabe, K. Kumagai, C. Sekine and I. Shirotani: Physica B **378-380** (2006) 230.

15) N. Takeda and M. Ishikawa: J. Phys.: Condens. Matter **15** (2003) 229.

16) K. Hachitani, H. Fukazawa, Y. Kohori, Y. Yoshimitsu, K. Kumagai, I. Watanabe, R. Giri, C. Sekine and I. Shirotani: *IPAP Conf. Series 5* (2004) 37.

17) W. M. Yuhasz, N. A. Frederick, P.-C. Ho, N. P. Butch, B. J. Taylor, T. A. Sayles and M. B. Maple: Phys. Rev. B **71** (2005) 104402.

18) K. Matsuhira, Y. Doi, M. Wakeshima, Y. Hinatsu, H. Amitsuka, Y. Shimaya, R. Giri, C. Sekine and I. Shirotani: J. Phys. Soc. Jpn. **74** (2005) 1030.

19) T. Ohama, H. Yasuoka, D. Mandrus, Z. Fisk and J. L. Smith: J. Phys. Soc. Jpn. **64** (1995) 2628.

20) Y. Nakai, K. Ishida, D. Kikuchi, H. Sugawara and H. Sato: J. Phys. Soc. Jpn. **74** (2005) 3370.